



Assessment of carrier transport properties of perovskite CsPbCl₃ single crystal with time-of-flight alpha-particle response

Qi-Hao Sun¹ · Zhou Wu¹ · Shu-Quan Wei¹ · Yu-Quan Wang¹ · Xu-Chang He¹ · Bao Xiao¹ · Nan-Nan Shen¹ · Jian-Fu Zhang² · Yi-Hui He¹

Received: 23 December 2024 / Revised: 7 February 2025 / Accepted: 10 March 2025 / Published online: 19 May 2026

© The Author(s), under exclusive licence to China Science Publishing & Media Ltd. (Science Press), Shanghai Institute of Applied Physics, the Chinese Academy of Sciences, Chinese Nuclear Society 2026

Abstract

All-inorganic CsPbCl₃ perovskite is a promising material for high-performance radiation detection owing to its extraordinary photoelectric properties and chemical stability. The critical challenge in developing wide-bandgap CsPbCl₃ perovskite lies in the quantitative assessment of its charge transport properties, which regulate its performance optimization. Herein, we report the first spectroscopic α particles using CsPbCl₃ detectors with asymmetric contact. CsPbCl₃ single crystals (ϕ 15 mm $\times$ 50 mm) were successfully grown using the Bridgman melt method and subsequently fabricated into Schottky-type Bi/CsPbCl₃/Au detectors. Owing to its high electrical resistivity of $1.25 \times 10^9 \Omega \cdot \text{cm}$, the CsPbCl₃ detector demonstrated a low dark current density ($\sim 870 \text{ nA/cm}^2$) and stable performance. The CsPbCl₃ detector was also capable of resolving both the α particle (5.5 MeV) and γ -ray (59.5 keV) peaks from the ²⁴¹Am radioactive isotope. Furthermore, the carrier transport properties of CsPbCl₃ were evaluated quantitatively by the time-of-flight technology using ²⁴¹Am α particle response, revealing the hole and electron mobilities as ~ 11.12 and $\sim 12.92 \text{ cm}^2 \cdot \text{V}^{-1} \cdot \text{s}^{-1}$, respectively. Meanwhile, the hole and electron mobility–lifetime products were obtained as $\sim 1.72 \times 10^{-4}$ and $\sim 1.04 \times 10^{-4} \text{ cm}^2 \cdot \text{V}^{-1}$, respectively. The planar CsPbCl₃ detector achieved an excellent energy resolution of $\sim 14.9\%$ at 122 keV under γ -ray exposure, which is the highest energy resolution reported to date for CsPbCl₃ detectors. This study highlights the considerable potential of inorganic perovskite detectors for radiation detection and provides a practical approach for the future development of perovskite materials.

Keywords CsPbCl₃ perovskite · Carrier transport · Bridgman method · Radiation detection · Semiconductor detector

This work was supported by the National Natural Science Foundation of China (No. U2267211), the National Key R&D Program of China (No. 2021YFF0502600), Suzhou Innovation and Entrepreneurship Leading Talent Plan Project (No. ZXL2022455), the Jiangsu Natural Science Foundation (No. BK20240822), China Postdoctoral Science Foundation (No. 2023M742531), the Open Fund of the State Key Laboratory of Integrated Optoelectronics (IOSKL2025KF06), and the State Key Laboratory of Functional Crystals and Devices (SKLFCD202501SIC). The authors contributed equally to this work.

✉ Yi-Hui He
yhhe@suda.edu.cn

¹ State Key Laboratory of Radiation Medicine and Protection, Collaborative Innovation Center of Radiological Medicine of Jiangsu Higher Education Institutions, and School for Radiological and Interdisciplinary Sciences (RAD-X), Soochow University, Suzhou 215123, China

² Northwest Institute of Nuclear Technology, Xi'an 710024, China

1 Introduction

The accurate detection of X-rays and γ -rays from radioactive sources at room temperature is critical for various applications, including industrial quality control, medical imaging diagnostics, and homeland security monitoring [1–3]. Precise detection enables enhanced imaging resolution, material inspection, and safety protocols. In this context, semiconductors with high radiation-stopping power and large carrier mobility–lifetime products are considered ideal owing to their potential for superior energy resolution. However, their practical implementation has faced persistent challenges for decades [4, 5]. This difficulty originates primarily from the low flux of γ -ray photons, which requires highly sensitive detection materials. Furthermore, most semiconductors are highly sensitive to the structural defects and chemical impurities that are inevitably formed during synthesis. These imperfections create charge-carrier traps, which significantly

degrade the detector performance by reducing the charge-collection efficiency and energy resolution.

Existing γ -ray detector materials are relatively scarce and face several critical issues. For instance, traditional materials, such as cadmium zinc telluride (CdZnTe) and high-purity germanium (HPGe), offer promising detection capabilities, but suffer from high production costs and limited bulk fabrication yields [6]. Although HPGe provides excellent resolution, it requires cryogenic cooling to reduce the thermal noise, complicating its operational setup [7]. The fabrication of CdZnTe is constrained by crystal growth challenges, which lead to material inhomogeneity and reduced device efficiency. Overcoming these material and fabrication limitations remains the primary focus of radiation detection research. Efforts have been directed toward developing new materials with fewer intrinsic defects, optimizing crystal growth techniques, and exploring cost-effective fabrication processes to create reliable and scalable γ -ray detectors suitable for room-temperature operation.

In recent years, metal halide perovskites have attracted widespread attention in fields ranging from optoelectronics to radiation detection largely because of their exceptional optoelectronic properties and tunable bandgaps [8–12]. Among them, lead halide perovskites with the general formula CsPbX_3 ($X = \text{Cl}, \text{Br}, \text{I}$) have demonstrated significant potential in high-efficiency solar cells [13], light-emitting devices [14], and photodetectors [15] owing to their high absorption coefficients, efficient charge transport, and remarkable defect tolerance [16, 17]. Notably, these materials can be chemically modified through halogen substitution, enabling the engineering of their electronic and optical properties to meet various application requirements.

Among the CsPbX_3 family members, CsPbI_3 is prone to a destructive phase transition to a yellow perovskitoid phase at room temperature, which hinders its long-term stability in practical applications [18, 19]. In contrast, CsPbBr_3 has been successfully grown with high crystalline purity and large single-crystal volume [20, 21]. Its intrinsic properties, including suitable bandgap, high absorption efficiency, and exceptional defect tolerance, make it a promising candidate for radiation detection. CsPbBr_3 detectors with asymmetric contacts demonstrated high resistivity and a mobility–lifetime ($\mu\tau$) product exceeding $10^{-3} \text{ cm}^2/\text{V}$ for holes. Furthermore, these detectors achieved remarkable energy resolution under hard X-rays and γ -rays, achieving an energy resolution of 3.9% under 122 keV ^{57}Co γ -rays [8].

Its counterpart, CsPbCl_3 , which is characterized by a wider bandgap, exhibits strong chemical stability under ambient conditions, making it particularly suitable for high-energy photon detection. Its high effective atomic number (69.8) and density (4.2 g/cm^3) contribute to its exceptional radiation-stopping power [22]. Although CsPbCl_3 is theoretically expected to possess favorable transport characteristics

owing to its ionic bonding and robust structural stability, comprehensive experimental data on its carrier mobility and lifetime are limited. Studies on CsPbCl_3 mobility–lifetime products and carrier mobility are crucial because these parameters directly influence the charge-collection efficiency and overall device performance.

Given its stability and promising theoretical transport properties, CsPbCl_3 is emerging as a potential high-performance semiconductor for radiation detection [23]. Its ability to withstand environmental degradation while maintaining its structural integrity makes it particularly appealing for long-term device applications. Understanding and optimizing its transport properties could pave the way for next-generation detectors capable of operating at room temperature with superior energy resolution. Further exploration of crystal growth techniques, defect passivation strategies, and device engineering could reveal the full potential of CsPbCl_3 in radiation detection and related optoelectronic applications. Thus, the continued investigation of its fundamental properties is imperative to advance its applicability in cutting-edge technologies.

In this study, we successfully utilized the Bridgman method to grow high-quality and large-volume ($\phi 15 \text{ mm} \times 50 \text{ mm}$) single crystals of CsPbCl_3 with excellent optical and structural uniformity. The superior quality of the crystal was demonstrated by its remarkable performance as a radiation detector. Employing an asymmetric electrode design, the CsPbCl_3 -based detectors demonstrated a stable dark current and an outstanding energy resolution of 14.2% for ^{241}Am α particles (5.5 MeV) and 14.9% for ^{57}Co γ -rays at room temperature (25 °C). Note that this represents the highest energy resolution reported thus far for a CsPbCl_3 detector. For the first time, the charge transport properties of CsPbCl_3 crystals were quantitatively characterized using the time-of-flight (ToF) method under ^{241}Am α particle excitation. The hole and electron mobilities were determined as ~ 11.12 and $\sim 12.92 \text{ cm}^2 \cdot \text{V}^{-1} \cdot \text{s}^{-1}$, respectively. Moreover, the hole and electron mobility–lifetime products, a critical figure of merit for detector materials, reached $\sim 1.72 \times 10^{-4}$ and $\sim 1.04 \times 10^{-4} \text{ cm}^2 \cdot \text{V}^{-1}$, respectively. These exceptional transport properties highlight the considerable potential of the all-inorganic perovskite CsPbCl_3 for room-temperature X/ γ -ray radiation detection with high resolution and reliability.

2 Experimental

2.1 Materials synthesis

CsPbCl_3 polycrystalline material was synthesized directly from high-purity precursor compounds, namely, cesium chloride (CsCl , Sigma-Aldrich, 99.999%) and lead chloride (PbCl_2 , Sigma-Aldrich, 99.999%), through a solid-state

reaction with a precise 1:1 stoichiometric ratio. The entire synthesis and crystal growth processes were conducted within the same sealed quartz ampoule (13 mm outer diameter, 10 mm inner diameter) to ensure a controlled environment and prevent contamination. The ampoule was initially evacuated to an ultrahigh vacuum level of less than 5×10^{-5} Pa and subsequently sealed to maintain a clean reaction atmosphere. The sealed ampoule containing the precursor materials was placed in a rocking furnace to facilitate uniform heating and promote the homogeneous mixing of the reactants. The synthesis was performed at 620 °C for 24 h, enabling the formation of high-quality CsPbCl₃ polycrystals. After the reaction, the resulting material exhibited a pale yellow appearance, indicating successful compound formation. This synthesis method ensured efficient crystal growth while minimizing the introduction of unwanted impurities, thereby rendering the produced CsPbCl₃ suitable for advanced optoelectronic and radiation detection applications.

2.2 Single-crystal growth

After synthesis, CsPbCl₃ single crystals were grown using the vertical Bridgman method, which is well suited for producing high-quality crystalline materials. A sealed quartz ampoule containing the synthesized material was carefully placed in a two-zone Bridgman furnace designed for controlled crystal growth. The upper and lower furnace zones were maintained at the temperatures of 650 °C and 300 °C, respectively, establishing a stable temperature gradient estimated to be in the range 15~20 °C/cm. This gradient is crucial for directing crystal growth along the desired axis. During the growth process, the ampoule was lowered at a slow and controlled rate of 0.5~1.0 mm/h to ensure uniform crystal formation while minimizing the incorporation of defects. After completing the growth process, the furnace was gradually cooled to room temperature at a controlled rate of 4~8 °C/h to reduce the thermal stress and prevent cracking. As the melting point of CsPbCl₃ is 611 °C, an overheating step was applied by maintaining the temperature at 620 °C for 10 h before starting the crystal growth. This step ensured the complete melting of the raw materials and improved the crystal quality by facilitating better mixing and uniformity of the melt. The ingot was cooled to 60 °C in 100 h. Owing to the existence of phase transitions, the ingot was cooled to room temperature at a cooling rate of 1 °C/h. Note that excessive temperature gradient, dropping speed, and cooling rate likely resulted in cracks and the final fracture of the ingots.

2.3 Structure and characterization of photoelectric properties

Powder X-ray diffraction (XRD) patterns were collected using an X'Pert PRO X-ray powder diffractometer equipped with a Cu K_α radiation source ($\lambda = 1.5406 \text{ \AA}$). The diffraction data were recorded over a 2θ range from 10° to 70° at a tube voltage of 40 kV and a tube current of 40 mA, ensuring high-quality diffraction patterns for phase identification and crystallinity evaluation. This analysis provides detailed structural information regarding the synthesized CsPbCl₃ crystals. The optical properties of the samples were examined using UV–vis spectroscopy performed on a UV-3150 spectrometer, covering a wavelength range of 400–900 nm. This enabled the precise measurement of the optical absorption edge and the determination of the bandgap energy. The electrical properties were evaluated by measuring the resistivity and dark current in the low bias voltage range of –1 to 1 V. The current–voltage (*I*–*V*) characteristics were recorded using a Keithley 6517B electrometer under dark conditions. The voltage was swept from 0 to +100 V and 0 to –100 V, following procedures established in our prior studies.

2.4 Device assembly

After slicing, the CsPbCl₃ crystals were meticulously polished to achieve smooth surfaces, which are essential for optimal electrode adhesion and device performance. To eliminate any residual surface contaminants, the polished crystals were thoroughly rinsed in toluene, an effective solvent for removing organic impurities and ensuring clean surfaces for subsequent electrode deposition. Asymmetric planar Bi/CsPbCl₃/Au detectors were constructed for device fabrication. Bismuth and gold electrodes were deposited onto the crystal surfaces via thermal evaporation using a precision-engineered shielding mask to define the electrode geometry. The electrode thickness ranged between 50 and 90 nm and was tailored to achieve optimal electrical contact and minimize resistance. The electrodes were designed to cover the entire surface area of the crystal, ensuring a uniform electric field distribution across the detector. Electrical connections to the external measurement circuitry were established by attaching copper wires to the electrodes, facilitating efficient signal transmission during device operation.

2.5 Detector performance characterization

In this study, 1 μCi ²⁴¹Am α particles and a ~14 μCi ⁵⁷Co γ-ray source were used to evaluate the detector performance. The primary decay from ²⁴¹Am to ²³⁷Np generates an α particle with the characteristic kinetic energy of 5.5 MeV, along with a γ-ray photon with the characteristic energy of 59.5 keV. The pulse shape information was simultaneously

recorded by connecting the preamplifier output to a high-speed waveform digitizer card. The signals from the preamplifier (eV-550) were further amplified and shaped using an amplifier (ORTEC 572A) with a gain of 0.8×200 and the shaping time constants of 2, 3, 6, and 10 μs . The final signals were subsequently evaluated using a dual 16 K input multichannel analyzer (ASPEC 927) and analog-to-digital converter, generating a response spectrum displayed on the MAESTRO-32 software. The energy resolution of the characteristic peak was determined using the full width at half maximum (FWHM, in keV) / (peak energy) $\times 100\%$. $\mu\tau$ was calculated using the single-carrier Hecht equation. The mobility was estimated using pulse height spectroscopy according to the equation $\mu = d^2/(t_r \cdot V)$, where t_r is the rise time, d is the thickness of the crystal, and V is the bias. Under a certain bias, the average value of the rise time distribution was used for t_r .

3 Results and discussion

Centimeter-sized CsPbCl_3 single crystals were grown from the melt using the vertical Bridgman method. Powder XRD experiments on the as-grown CsPbCl_3 crystals matched well with the standard card for CsPbCl_3 (PDF#18-0366). The ideal crystal composition was estimated to be Cs: Pb: Cl = 1: 1: 3 from energy-dispersive X-ray spectroscopy (EDS) measurements (Fig. S1 and Table S1). No peaks related to the impurity phases were observed, indicating that the crystal was a pure CsPbCl_3 single crystal (Fig. 1a). Both the as-grown crystal ingot and the polished wafer had a pale yellow color with excellent optical transparency (Fig. S2). The optical transmission exceeded 70% when the wavelength of the incident light ranged from 300 to 900 nm (Fig. 1b). The high transmission confirms that the as-grown single crystals possess negligible absorption centers below the bandgap. This observation enabled the calculation of the absorption

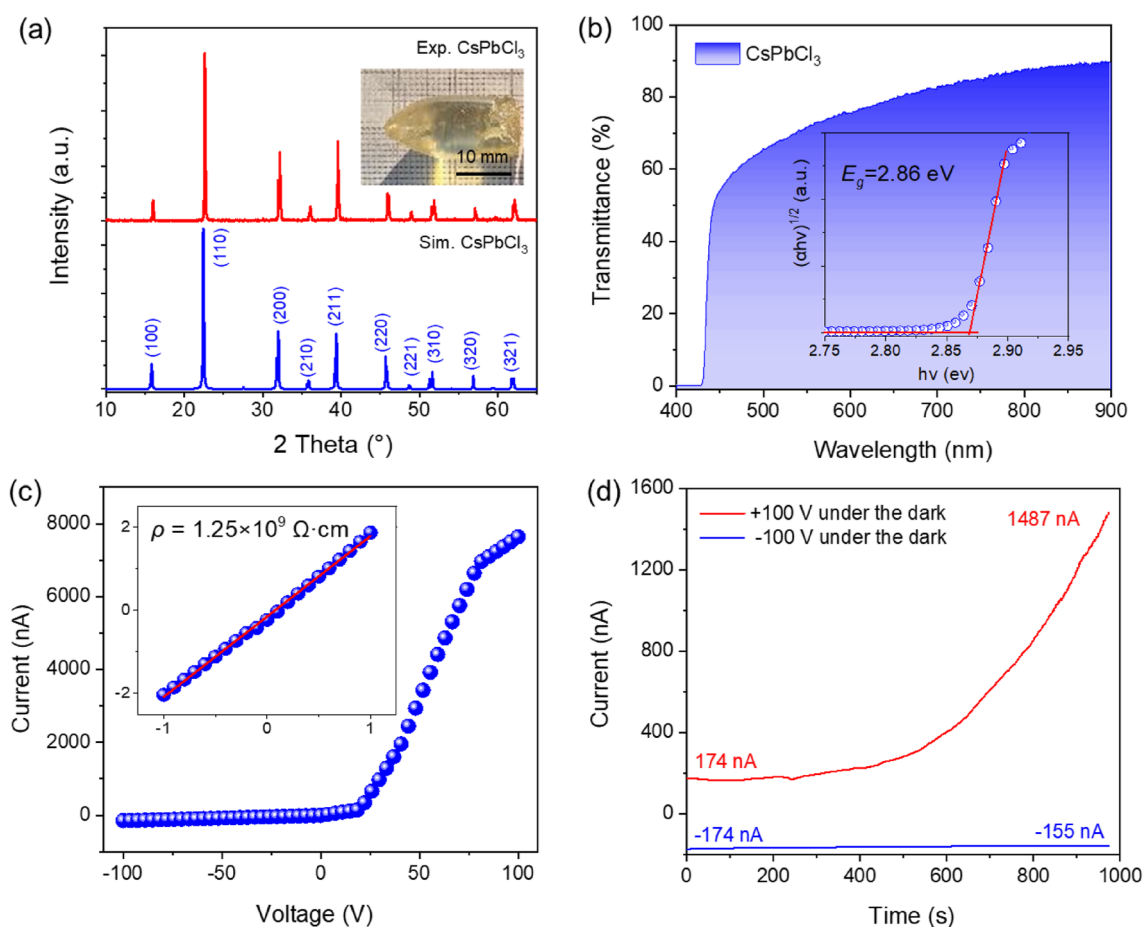


Fig. 1 (Color online) **a** Powder XRD patterns of the CsPbCl_3 crystal. The inset corresponds to the CsPbCl_3 ingot. **b** Transmission spectra for the CsPbCl_3 single crystal. Inset: Tauc plot showing the direct bandgap of 2.86 eV. **c** Typical I - V characteristic curve of a Schottky-

type Bi/ CsPbCl_3 /Au detector. **d** Temporal characteristics of the Schottky-type Bi/ CsPbCl_3 /Au detector under positive (forward) and negative (reverse) applied bias conditions

coefficient α , thereby facilitating the determination of the bandgap E_g of the CsPbCl₃ crystals near the absorption cut-off. The optical absorption edge extracted from the transmission spectrum was 434 nm. The inset of Fig. 1b shows the Tauc plot used to extract the direct bandgap E_g of CsPbCl₃ using the following equation:

$$(\alpha h\nu)^2 \propto (h\nu - E_g), \quad (1)$$

where $h\nu$ is the photon energy. Extrapolating these calculations revealed that the CsPbCl₃ samples have E_g values close to 2.86 eV.

A CsPbCl₃ planar detector with asymmetric electrodes was prepared using evaporated Bi and Au metals. Bi metal has a relatively low work function ($\phi_{\text{Bi}} \sim 4.2$ eV) and can form a large potential barrier preventing hole injection from the electrode, whereas Au, which possesses a high work function ($\phi_{\text{Au}} \sim 5.1$ eV), generates a large potential barrier for electrons. The I - V curve of the as-prepared Bi/CsPbCl₃/Au device exhibited asymmetrical characteristics (Fig. 1c) because of the dissimilar Schottky barriers under forward and reverse biases. The electrical properties were characterized using I - V tests. As demonstrated by the I - V curve, the results align well with the Ohmic law at a bias of ± 1 V, and these data can be used to calculate the resistivity according to the following equation:

$$\rho = \frac{RS}{L}, \quad (2)$$

where ρ is the resistivity, S is the contact area of 4 mm $\times$ 5 mm, L is the sample thickness (2 mm), and R is the resistance. In particular, the electrical resistivity of CsPbCl₃ obtained by fitting was $1.25 \times 10^9 \Omega \cdot \text{cm}$. The dark current density of this device was ~ 870 nA/cm² at -1000 V/cm, in contrast to ~ 7.4 $\mu\text{A}/\text{cm}^2$ at 1000 V/cm. The temporal stability of the dark current is vital for maintaining the high stability of the perovskite detector. For the Schottky-type Bi/CsPbCl₃/Au detector, the density of the dark current on the reverse side tended to decrease slightly with time, but it appeared to reach a limit at -155 nA under -100 V bias (Fig. 1d). By contrast, the dark current on the forward side continued to increase for 950 s, which increased the background noise and degraded the energy resolution and detector stability. The photoresponse of the Bi/CsPbCl₃/Au detector was measured using a 420 nm LED at -10 V, where the ratio of the photocurrent to the dark current was larger than 65, as shown in Fig. S3.

A schematic illustrating the charge-carrier transport process induced by α particles in the CsPbCl₃ crystal is shown in Fig. 2a. To ensure better collimation of the α radiation emitted from the ²⁴¹Am source, rubber putty was employed as the encapsulating material. This configuration enabled a more directional incidence of the emitted α particles onto

the detector surface, minimizing scattering and improving measurement precision. Upon irradiation, the interaction of α particles with the CsPbCl₃ crystal generates electron-hole pairs owing to ionization. Under the influence of an externally applied electric field, electrons drift toward the anode, whereas holes migrate toward the cathode, facilitating charge collection. The Bi/CsPbCl₃/Au detector, based on a Schottky-type structure, successfully resolved the full energy spectrum of a collimated ²⁴¹Am α radiation source. This marked a significant achievement, as for the first time, the CsPbCl₃ detector distinctly resolved the primary high-energy α particle peak alongside the associated low-energy γ -ray peak. The appearance of these two distinct peaks corresponds to the two radiation products of the ²⁴¹Am decay: the emitted α particles and the accompanying γ -ray photons. The ability to separate these two radiation products highlights the potential of CsPbCl₃ as a material for high-resolution radiation detection applications. The bias dependence of the energy spectra for α -particle detection was further examined, and the corresponding results are shown in Fig. 2b and 2c for hole and electron collection, respectively. An increase in the applied bias voltage led to an enhanced charge-collection efficiency, as evidenced by the prominent peak shift toward higher channel numbers. This behavior indicates improved carrier extraction owing to the stronger electric field, which accelerates charge carriers and reduces recombination losses. Interestingly, a notable disparity was observed between the electron and hole collection efficiencies. Specifically, the electron response exhibited only weak shoulders in the spectra without an apparent peak resolution. This asymmetry suggests that significant electron trapping occurred within the CsPbCl₃ crystal, likely owing to intrinsic defects or trap states. In contrast, the hole collection efficiency was substantially higher, leading to more distinct peak formation in the spectra. This result underscores the importance of mitigating charge-trapping effects, particularly for electrons, to achieve optimal detector performance. Future improvements in crystal growth techniques and device engineering may further enhance the potential of this material for advanced radiation detection applications. Under an applied voltage of -250 V, the Schottky-type CsPbCl₃ detector achieved the energy resolutions of $\sim 14.2\%$ for 5.5 MeV α particles and $\sim 20.5\%$ for 59.5 keV γ -rays (Fig. 2d), which is the maximum α -particle spectral resolution for a CsPbCl₃ single-crystal detector. This is also the highest γ -ray detection energy resolution currently reported for a CsPbCl₃ detector. The excellent spectral responses were attributed to the prominent carrier transport properties, and the ToF technology was adopted to evaluate the charge-carrier mobility of the CsPbCl₃ crystal.

Figure 3a shows the simulated paths and stopping ranges of α particles with an energy of 5.5 MeV in CsPbCl₃ single crystals, obtained through Monte Carlo calculations using

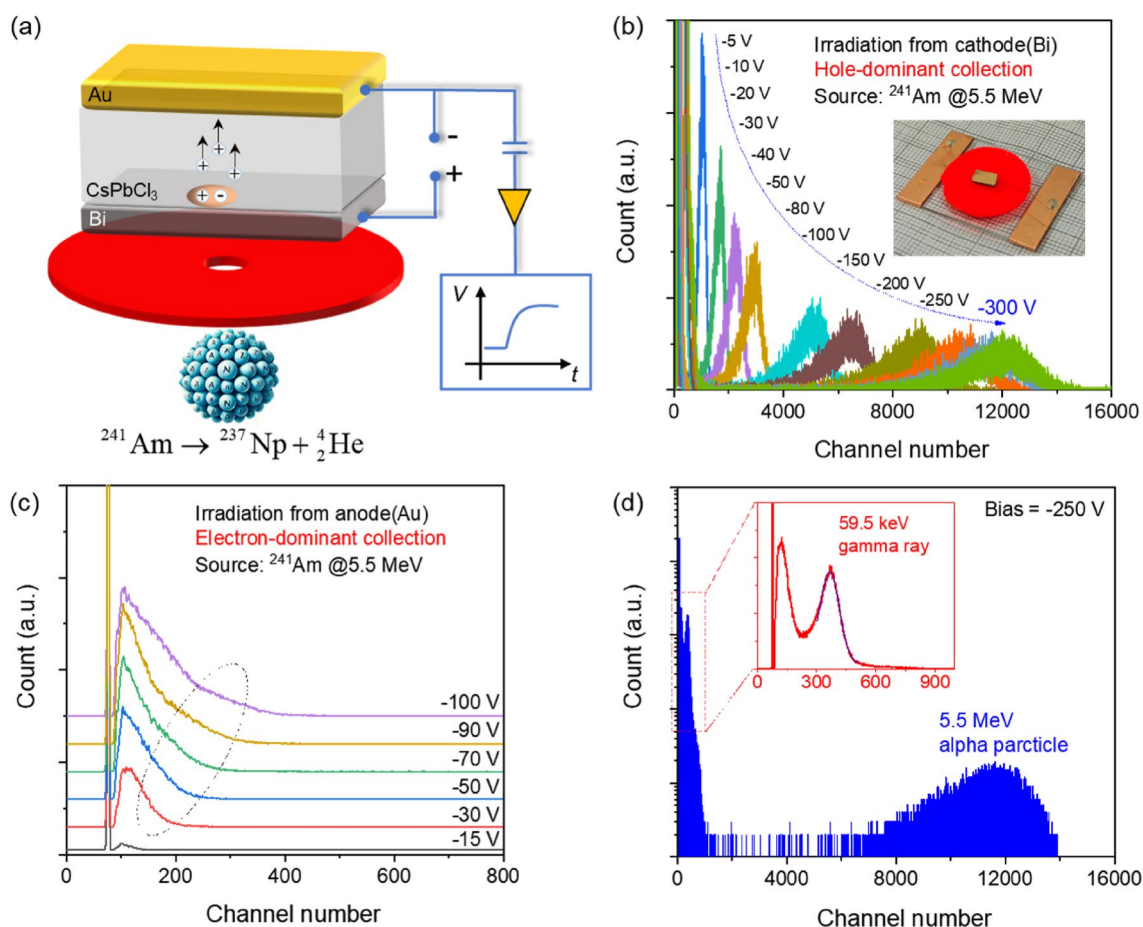


Fig. 2 (Color online) **a** Schematic of the transport and signal generation of streamers under α particles. Bias-dependent ^{241}Am α particle spectra under negative **b** and positive **c** voltages using a Schottky-type Bi/CsPbCl₃/Au detector. As indicated in the insert, the dimen-

sions of the crystal are 5 mm $\times$ 4 mm $\times$ 1 mm. **(d)** ^{241}Am α particle spectrum resolved concurrently by a Schottky-type Bi/CsPbCl₃/Au detector at -250 V

the SRIM software. This simulation provides crucial insights into the interaction dynamics of α particles within a crystal lattice. As shown in Fig. 3b, the depth distributions of α particles reveal a shallow penetration depth of approximately 27.4 μm . This limited penetration results in the majority of electron-hole pairs being generated and concentrated near the cathode region of the crystal. Consequently, the detected charge signal is predominantly attributed to the drift of a single-carrier type with either positive or negative polarity, depending on the orientation of the applied electric field. The induced transit current generated by these drifting carriers was converted into a voltage pulse using a charge-sensitive preamplifier. The preamplifier output was subsequently digitized using a high-speed waveform digitizer card for precise signal collection and analysis. The carrier mobility was evaluated by measuring the rise time of the voltage pulse as a function of the applied bias voltage. The drift velocities (v) of the carriers were determined using the following equation:

$$v = \frac{d}{t_r}, \quad (3)$$

where d represents the thickness of the CsPbCl₃ crystal, and t_r is the rise time measured between the 10% and 90% amplitude points of the signal pulse. Typical voltage pulses extracted from the preamplifier at an applied bias of -300 V are shown in Fig. 3c. These pulses provide direct evidence of charge-carrier transport behavior within the crystal under an external electric field. Furthermore, Fig. 3d shows the voltage pulses induced by α particles at various applied bias voltages, specifically for hole transport. As the applied voltage increased, the amplitude of the preamplifier signal increased, whereas the rise time decreased. This behavior reflects the accelerated drift velocity of the charge carriers owing to the stronger electric field, which enhances the charge-collection efficiency. To gain a deeper understanding of the charge transport properties in the Bi/CsPbCl₃/Au Schottky detector, it is important to emphasize that the

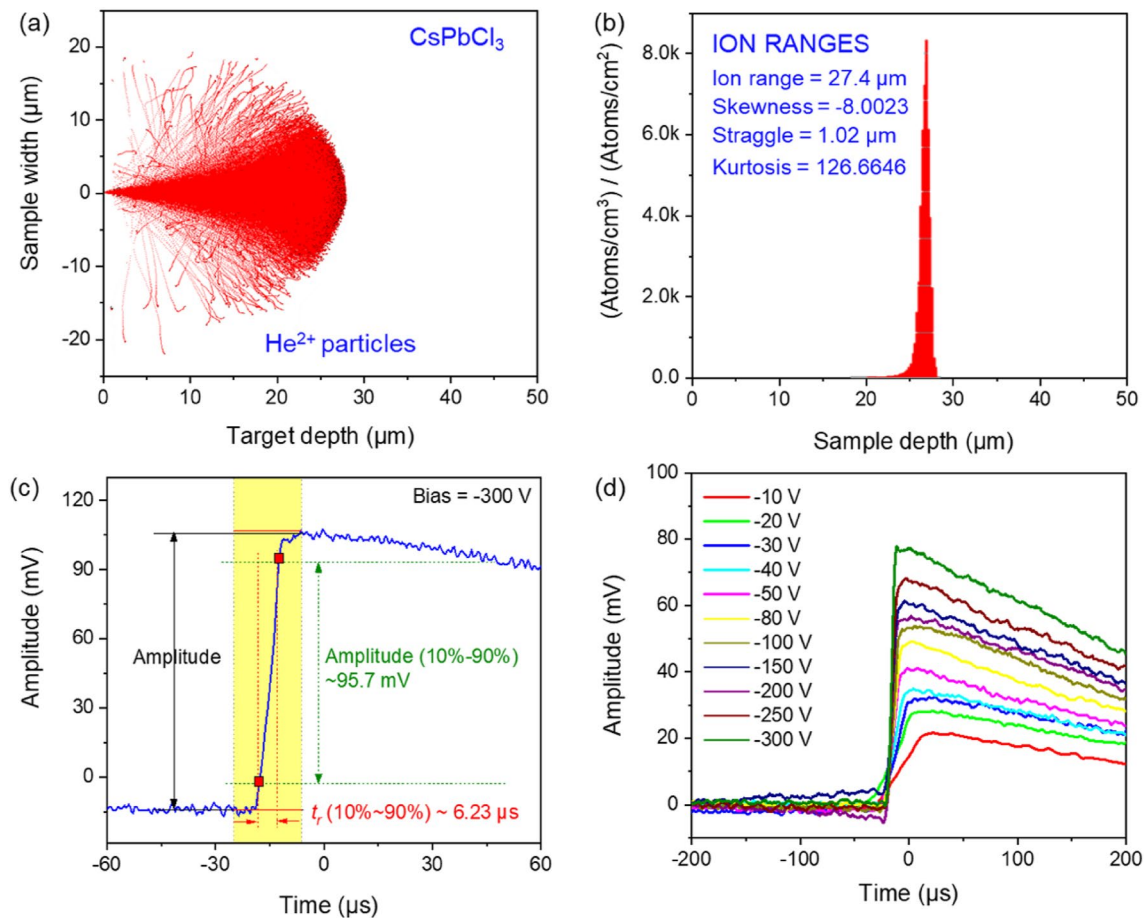


Fig. 3 (Color online) **a** Stopping and range of α particles with the energy of 5.5 MeV in CsPbCl₃ single crystals by Monte Carlo simulation. **b** Depth distributions of α particles in CsPbCl₃. **c** Pulse signal

of the preamplifier including amplitude and rise time under α particles at -300 V. **d** Hole pulse signal of the preamplifier under various biases

device operates in the pulse mode, where each radioactive event is independently collected and processed. This methodology enables the extraction of key charge transport parameters through a statistical analysis of the raw transient pulses produced by the detector. The transient pulses were carefully analyzed using a preamplifier to extract critical characteristics, such as the amplitude and rise times of the signals, which were subsequently categorized into hole and electron drift contributions. To distinguish the charge-collection modes dominated by holes and electrons in the crystal, we irradiated the device with ^{241}Am α particles and ^{57}Co γ rays from the anode and cathode sides, respectively, as shown in Fig. S4. Notably, the bias voltage applied to the device remained constant throughout the testing process, with only the direction of the incident radiation being altered. Consequently, signal flooding owing to an increase in the dark current under a positive-bias state is not a concern. The device was consistently operated in a low-dark-current state with a negative bias voltage.

As shown in Fig. 4 and Fig. S5, the distributions of both the amplitude and rise times were analyzed across 2000 events, providing insights into the drift dynamics of the charge carriers within the CsPbCl₃ crystals. An interesting trend observed in these analyses was a shift in the peak position of the signal amplitude distribution as the applied voltage increased Fig. 4a. Specifically, the peak of the amplitude distribution shifted to higher values with increasing voltage, suggesting that the charge-collection efficiency improved at higher electric fields. This behavior is consistent with the expected response of semiconductor detectors under bias, where higher voltages generally enhance the drift velocity of charge carriers, thus leading to stronger signals. In addition, the corresponding rise time distributions narrowed as the voltage increased, as shown in Fig. 4b. This narrowing effect indicates faster charge-collection times, as the average rise time decreased with increasing applied voltage. These observations are further supported by a detailed analysis of the experimental data, which reveals an evident correlation between the voltage

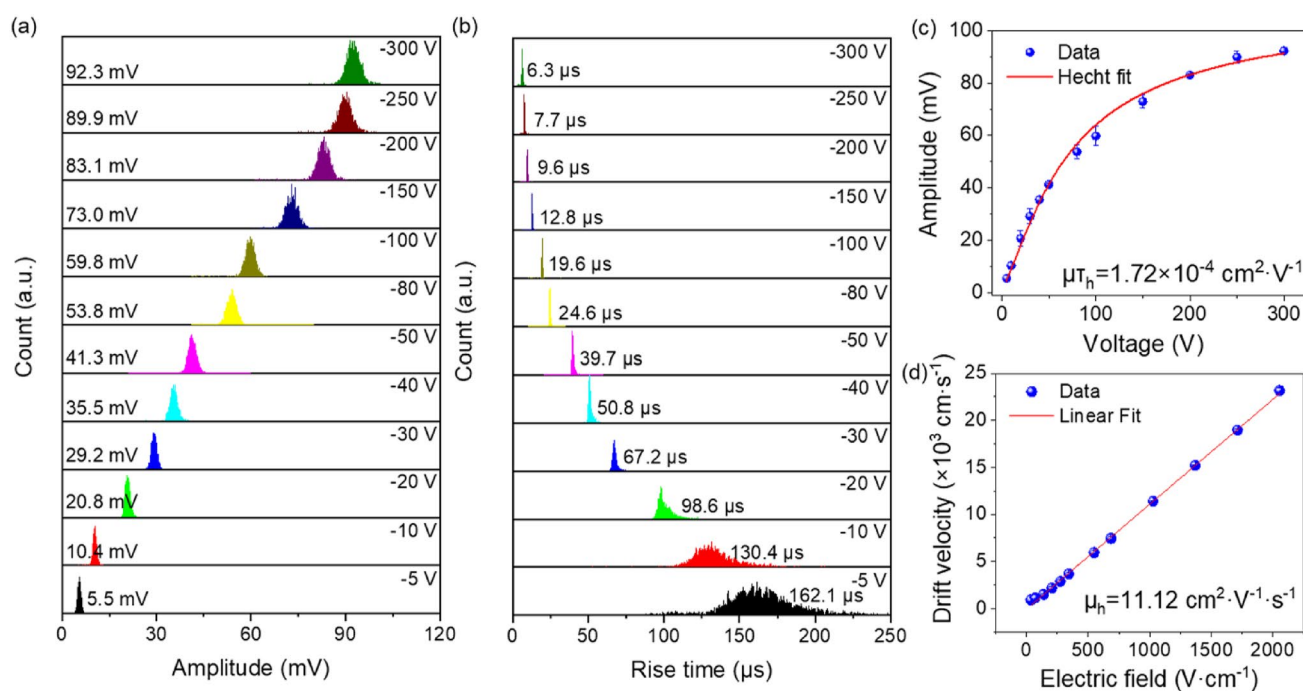


Fig. 4 (Color online) **a** Amplitude distribution (2000 events) attributed to hole drift based on the transient pulse analysis for ^{241}Am α particles. **b** Rise time distribution (2000 events) attributed to hole

drift based on the transient pulse analysis for ^{241}Am α particles. **c** Mobility–lifetime product calculation for holes according to the single-carrier Hecht equation. **d** Hole mobility calculation for CsPbCl_3

and charge transport properties of the detector. To quantify the charge transport characteristics, the experimental mobility–lifetime product ($\mu\tau$) was calculated using the single-carrier Hecht equation. This equation provides a relationship between the signal amplitude and the applied voltage, which can be used to deduce the product of the charge-carrier mobility (μ) and lifetime (τ). The calculated $\mu\tau$ values for the hole and electron carriers were $1.72 \times 10^{-4} \text{ cm}^2 \cdot \text{V}^{-1}$ and $1.04 \times 10^{-4} \text{ cm}^2 \cdot \text{V}^{-1}$, respectively, as shown in Fig. 4c and S5c. These values are significant because they enable the evaluation of the charge transport efficiency in the CsPbCl_3 material, which is crucial for its performance as a radiation detector. Furthermore, the mobility values of the hole and electron carriers were calculated separately as approximately $11.12 \text{ cm}^2 \cdot \text{V}^{-1} \cdot \text{s}^{-1}$ and $12.92 \text{ cm}^2 \cdot \text{V}^{-1} \cdot \text{s}^{-1}$, respectively, as shown in Fig. 4d and Fig. S5d. These mobility values are comparable to those reported in a previous study, reinforcing the validity of the experimental approach and the consistency of the material properties.

Note that the mobility values calculated in this study were somewhat lower than those obtained using ^{241}Am γ -rays in previous experiments. This difference in mobility values can be attributed to the distinct interaction depths between the ^{241}Am α particles and the material. The interaction depth of α particles is much smaller than that of γ -rays, resulting in a reduced range of charge-carrier transport and lower signal

amplitude. The penetration length of ^{241}Am α particles in CsPbCl_3 is approximately $27.4 \mu\text{m}$, which is much smaller than the thickness of the detector; thus, the ^{241}Am α particles interact with a relatively small portion of the detector material. This limitation of the interaction depth of α -particles partially explains the lower μ values observed in this study. In addition to the mobility calculations, the lifetime of the hole carriers (τ_h) in CsPbCl_3 was determined based on the previously calculated values of μ_h and $\mu\tau_h$. The hole lifetime was determined to be approximately $15.47 \mu\text{s}$, which is significantly longer than the hole lifetime observed in several other compound semiconductors. This value is comparable to the hole lifetime of CsPbBr_3 , another perovskite material that has demonstrated strong potential for radiation detection [9]. The longer lifetime of the holes is particularly important because it suggests that the CsPbCl_3 material can sustain charge carriers for a longer duration, enabling more efficient charge collection and, ultimately, a higher detection sensitivity. These results demonstrate the excellent charge transport properties of the CsPbCl_3 crystals grown via the Bridgman melting method, confirming their considerable potential for applications in room-temperature radiation detection. The long hole lifetime, high carrier mobility, and strong signal response to the applied voltage suggest that CsPbCl_3 is an ideal candidate for advanced radiation detection technologies.

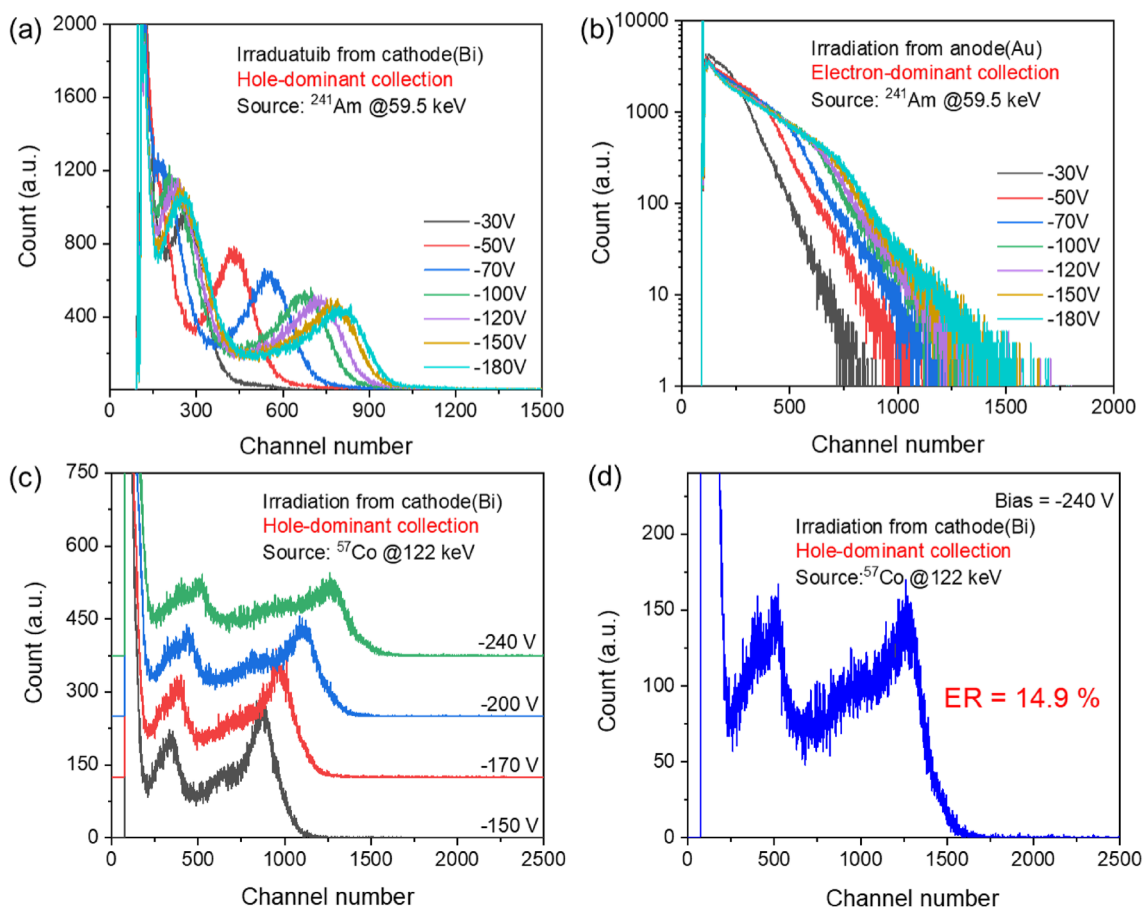


Fig. 5 (Color online) γ -ray response by the Schottky-type CsPbCl₃ detector under **a** hole dominant transport and **b** electron dominant transport collection under ^{241}Am γ -rays. **c** ^{57}Co γ -ray spectrum by

the same CsPbCl₃ crystal under the same conditions. **d** ^{57}Co γ -ray response in 3 min under the applied voltage of -240 V with a shaping time of $10\text{ }\mu\text{s}$

The γ -ray spectroscopic response of the Schottky-type CsPbCl₃ detector is shown in Fig. 5, providing detailed insights into its performance when irradiated with γ -rays. The experiment utilized a noncollimated ^{241}Am γ -ray source ($\sim 1\text{ }\mu\text{Ci}$) irradiated from the upper Bi electrode. Remarkably, the fine spectrum of the ^{241}Am isotope was fully resolved by the Schottky-type Bi/CsPbCl₃/Au detector in both the hole and electron collection configurations. This ability to resolve the γ -ray spectrum highlights the exceptional performance of CsPbCl₃ as a radiation detector, and provides a clear and reliable energy spectrum that can be used for various radiation detection applications. The γ -ray energy spectra derived from hole- and electron-dominated charge collection are shown in Fig. 5a and 5b, respectively. These figures illustrate the bias dependence of the γ -ray energy spectra with a noticeable difference between the hole and electron collection configurations. As the applied bias voltage increased, an apparent improvement in the charge transport was observed, as evidenced by the peak shift to greater channel numbers. This shift indicates an enhanced

charge-collection efficiency at higher bias voltages, which corresponds to the increased drift velocity of the charge carriers under stronger electric fields. This trend is expected in most semiconductor detectors where higher voltages facilitate the movement of charge carriers, leading to more efficient signal generation. In the hole collection configuration, the CsPbCl₃ detector achieved an impressive energy resolution of 20.1% for ^{241}Am γ -rays at an applied bias of -180 V . This result is notable because the energy resolution is a critical factor in evaluating the performance of radiation detectors. A high-energy resolution ensures that the detector can distinguish between the different energy levels of the incoming radiation, which is essential for identifying and quantifying radioactive isotopes. However, the electron collection configuration demonstrated an inferior performance compared with hole collection. In the electron collection mode, the detector exhibited only a counting response to the γ -rays with visible spectral shoulders but no apparent spectral resolving ability. This lack of resolution in the electron collection mode is presumed to be due to the charge

trapping of electrons in the CsPbCl₃ material. Charge trapping occurs when charge carriers are captured by defects or impurities in a material, which reduces their mobility and prevents efficient charge collection. This is a known issue in several semiconductor detectors and suggests that the further optimization of the CsPbCl₃ material is required to reduce electron trapping and improve its performance in the electron collection mode.

In addition to the ²⁴¹Am γ -rays, the γ -ray energy spectra of the ⁵⁷Co γ -ray source (~ 14 μ Ci) were measured, as shown in Fig. 5c. The ⁵⁷Co γ -rays, which have an energy of 122 keV, provide additional insights into the performance of the detector in terms of the energy resolution and spectral features. Notably, the Pb escape γ -ray peak, which is a well-known feature in γ -ray spectra, was observed at a channel number of approximately 336 when the applied bias was greater than -150 V. The Pb escape X-ray peak occurs when a γ -ray interacts with the detector material and generates an electron that causes the emission of low-energy X-rays from the lead component of the detector. The detection of this peak is a characteristic feature of high-resolution γ -ray spectroscopy, and its observation further confirms the ability of the CsPbCl₃ detector to resolve the fine spectral features. At a higher applied bias of -240 V, the Schottky-type CsPbCl₃ detector achieved an energy resolution of 14.9% for the 122 keV γ -rays from the ⁵⁷Co source, as shown in Fig. 5d. This represents the highest energy resolution for 122 keV γ -rays reported for CsPbCl₃ crystals to date, which is a significant achievement for wide-bandgap materials, such as CsPbCl₃. The ability to achieve such a high-energy resolution in a material with a relatively wide bandgap is impressive, as wide-gap materials typically struggle with charge transport and spectral resolution owing to the presence of defects and poor charge-carrier mobility. The excellent energy resolution achieved in this study demonstrates the potential of CsPbCl₃ for high-performance γ -ray detection. Note that the CsPbCl₃ crystals used in this study were prepared without the intentional purification of the starting binary precursor compounds or CsPbCl₃ material. This is in contrast to the preparation of other high-performance radiation detectors, such as CdZnTe (CZT), where the intentional purification of the precursor materials is typically required to achieve detector-grade performance [2, 24, 25]. The lack of purification steps during the preparation of CsPbCl₃ highlights the inherent defect-tolerant nature of this material, which is a key advantage of perovskite materials. This characteristic makes CsPbCl₃ particularly attractive for use in radiation detectors because it simplifies the fabrication process and reduces costs compared with other conventional semiconductor materials. By contrast, other conventional halide semiconductors, such as HgI₂ and TlBr, require multistep and complicated purification processes to

achieve the necessary material quality for radiation detection [26]. These purification steps often involve expensive and time-consuming procedures, which increase the overall cost and complexity of the detector fabrication process. The simplicity of preparing CsPbCl₃ for radiation detection without the need for extensive purification further emphasizes its potential as a practical and cost-effective material for radiation detection applications. Overall, the results of the γ -ray spectroscopic response demonstrate the exceptional performance of the Schottky-type CsPbCl₃ detector. The ability to achieve high-energy resolution and spectral features with minimal preparation steps demonstrates the potential of CsPbCl₃ as a leading material for radiation detection with possible applications in nuclear security, medical imaging, and environmental monitoring.

4 Summary

The wide-bandgap CsPbCl₃ perovskite has considerable potential for γ -ray detection at room temperature, similar to CsPbBr₃. We successfully utilized the Bridgman melt method to grow centimeter-sized detector-grade crystals with exceptional optical and physical properties. The carrier transport properties of CsPbCl₃ crystals were characterized for the first time using α particles via the ToF technology. An asymmetric electrode design (Bi/CsPbCl₃/Au) was implemented to maintain a low and stable dark current. The as-prepared detector exhibited a stable and low dark current (~ 870 nA/cm²), even under a high electric field (1000 V/cm). The Schottky-type Bi/CsPbCl₃/Au detector resolved both the α particle spectrum and coincident γ -ray spectrum from a ²⁴¹Am radiation source. The energy resolution for the 5.5 MeV α particle peak was $\sim 14.2\%$. According to the α particle spectrum and corresponding rise time distribution, the hole and electron mobilities were calculated as 11.12 and 12.92 cm² · V⁻¹ · s⁻¹, respectively. The CsPbCl₃ detector exhibited a high hole mobility–lifetime ($\mu\tau$)_h product of $\sim 1.72 \times 10^{-4}$ cm²/V compared with the electron mobility–lifetime ($\mu\tau$)_e product of $\sim 1.04 \times 10^{-4}$ cm² · V⁻¹. Furthermore, an excellent energy resolution of $\sim 14.9\%$ was achieved using ⁵⁷Co γ -rays with a characteristic energy of 122 keV. Overall, CsPbCl₃ is the first chloride-based semiconductor reported to date with excellent γ -ray detection capabilities in the bulk form. Most other materials considered promising for γ -ray detection exhibit poor counting properties, lack energy resolution, and ultimately fail to satisfy the required standards. CsPbCl₃ is not only the second member of the all-inorganic perovskite family, but also one of the few semiconductor materials across various families that can achieve an outstanding energy resolution. These

results highlight the exceptional detector performance and charge transport properties of CsPbCl₃ single crystals, highlighting their potential for broad applications in room-temperature radiation detection.

Supplementary Information The online version contains supplementary material available at <https://doi.org/10.1007/s41365-026-01965-8>.

Author contributions All authors contributed to the study conception and design. Material preparation, data collection and analysis were performed by Qi-Hao Sun, Zhou Wu, Shu-Quan Wei, Yu-Quan Wang, Xu-Chang He, Bao Xiao, Nan-Nan Shen, Jian-Fu Zhang, and Yi-Hui He. The first draft of the manuscript was written by Qi-Hao Sun, and all authors commented on previous versions of the manuscript. All authors read and approved the final manuscript.

Data availability The data that support the findings of this study are openly available in Science Data Bank at <https://cstr.cn/31253.11.sciencedb.j00186.00886> and <https://www.doi.org/10.57760/sciencedb.j00186.00886>.

Declarations

Conflict of interest The authors declare that they have no competing interests.

References

1. S.Y. Zhang, Z.X. Wang, H.B. Yang et al., Hformer: highly efficient vision transformer for low-dose CT denoising. *Nucl. Sci. Tech.* **34**, 61 (2023). <https://doi.org/10.1007/s41365-023-01208-0>
2. P. Huang, Measurement of air kerma rate and ambient dose equivalent rate using the $G(E)$ function with hemispherical CdZnTe detector. *Nucl. Sci. Tech.* **29**, 35 (2018). <https://doi.org/10.1007/s41365-018-0375-3>
3. S. Wang, J.H. Guo, Y. Zhang et al., High-resolution pixelated CdZnTe detector prototype system for solar hard X-ray imager. *Nucl. Sci. Tech.* **30**, 42 (2019). <https://doi.org/10.1007/s41365-019-0571-9>
4. X. Zhang, F. Li, Y. Hao et al., Improved energy resolution by weighting potential optimization in CsPbBr₃ pixelated gamma-ray detector. *IEEE Trans. Electron Devices* **70**, 5190–5195 (2023). <https://doi.org/10.1109/TED.2023.3307506>
5. Q. Sun, B. Ge, B. Xiao et al., High-performance industrial-grade CsPbBr₃ single crystal by solid-liquid interface engineering. *Adv. Sci.* **10**, 2302236 (2023). <https://doi.org/10.1002/adv.202302236>
6. J.R. Macri, L.A. Hamel, M. Julien et al., Single-sided CZT strip detectors. *IEEE Trans. Nucl. Sci.* **51**, 2453–2460 (2004). <https://doi.org/10.1109/TNS.2004.836091>
7. C.D. Fan, G.Q. Zeng, H.W. Deng et al., Artificial neural network-based method for discriminating Compton scattering events in high-purity germanium γ -ray spectrometer. *Nucl. Sci. Tech.* **35**, 34 (2024). <https://doi.org/10.1007/s41365-024-01392-7>
8. Y. He, L. Matei, H.J. Jung et al., High spectral resolution of gamma-rays at room temperature by perovskite CsPbBr₃ single crystals. *Nat. Commun.* **9**, 1609 (2018). <https://doi.org/10.1038/s41467-018-04073-3>
9. Z. Lü, G. Wei, H. Wang et al., New flexible CsPbBr₃-based scintillator for X-ray tomography. *Nucl. Sci. Tech.* **33**, 98 (2022). <https://doi.org/10.1007/s41365-022-01085-z>
10. C.C. Stoumpos, C.D. Malliakas, J.A. Peters et al., Crystal growth of the perovskite semiconductor CsPbBr₃: a new material for high-energy radiation detection. *Cryst. Growth Des.* **13**, 2722–2727 (2013). <https://doi.org/10.1021/cg400645t>
11. Y. Wang, Q. Zhang, A characterization study on perovskite X-ray detector performance based on a digital radiography system. *Nucl. Sci. Tech.* **34**, 69 (2023). <https://doi.org/10.1007/s41365-023-01220-4>
12. Q. Xu, H. Wei, W. Wei et al., Detection of charged particles with a methylammonium lead tribromide perovskite single crystal. *Nucl. Instrum. Meth. A* **848**, 106–108 (2017). <https://doi.org/10.1016/j.nima.2016.12.062>
13. B. Xue, L. Zhang, Z. Li et al., Property degradation of mixed-cation perovskite films and solar cells irradiated with protons. *Nucl. Instrum. Meth. B* **526**, 29–35 (2022). <https://doi.org/10.1016/j.nimb.2022.06.012>
14. W. Wang, B. Wang, Q. Xu et al., Elaboration, electrical and X-ray characterization of potassium-chloride passivated MAPbI₃. *Nucl. Instrum. Meth. A* **1042**, 167398 (2022). <https://doi.org/10.1016/j.nima.2022.167398>
15. W. Yan, B. Duan, Z. Zhu et al., Organic-inorganic hybrid perovskite scintillator for high-resolution X-ray imaging. *Nucl. Instrum. Meth. B* **546**, 165159 (2024). <https://doi.org/10.1016/j.nimb.2023.165159>
16. H. Dong, C. Zhang, X. Liu et al., Materials chemistry and engineering in metal halide perovskite lasers. *Chem. Soc. Rev.* **49**, 951–982 (2020). <https://doi.org/10.1039/C9CS00598F>
17. Z. Xiao, Z. Song, Y. Yan, From lead halide perovskites to lead-free metal halide perovskites and perovskite derivatives. *Adv. Mater.* **31**, 1803792 (2019). <https://doi.org/10.1002/adma.201803792>
18. B. Li, Y. Zhang, L. Fu et al., Surface passivation engineering strategy to fully-inorganic cubic CsPbI₃ perovskites for high-performance solar cells. *Nat. Commun.* **9**, 1076 (2018). <https://doi.org/10.1038/s41467-018-03169-0>
19. B.B. Zhang, X. Liu, B. Xiao et al., High-performance X-ray detection based on one-dimensional inorganic halide perovskite CsPbI₃. *J. Phys. Chem. Lett.* **11**, 432–437 (2019). <https://doi.org/10.1021/acs.jpclett.9b03523>
20. H. Zhang, F. Wang, Y. Lu et al., High-sensitivity X-ray detectors based on solution-grown caesium lead bromide single crystals. *J. Mater. Chem. C* **8**, 1248–1256 (2020). <https://doi.org/10.1039/C9TC05490A>
21. Y. He, M. Petryk, Z. Liu et al., CsPbBr₃ perovskite detectors with 1.4% energy resolution for high-energy γ -rays. *Nat. Photonics* **15**, 36–42 (2021). <https://doi.org/10.1038/s41566-020-00727-1>
22. Y. He, C.C. Stoumpos, I. Hadar et al., Demonstration of energy-resolved γ -ray detection at room temperature by the CsPbCl₃ perovskite semiconductor. *J. Am. Chem. Soc.* **143**, 2068–2077 (2021). <https://doi.org/10.1021/jacs.0c12254>
23. Z. Rao, W. Liang, H. Huang et al., High sensitivity and rapid response ultraviolet photodetector of a tetragonal CsPbCl₃ perovskite single crystal. *Opt. Mater. Express* **10**, 1374 (2020). <https://doi.org/10.1364/OME.388429>
24. Y. Du, J. LeBlanc, G.E. Possin et al., Temporal response of CZT detectors under intense irradiation. *IEEE Trans. Nucl. Sci.* **50**, 1031–1035 (2003). <https://doi.org/10.1109/TNS.2003.815348>
25. R. Wu, Y. Kang, D. Wei et al., Energy spectrum correction and carrier mobility calculation of CdZnTe pixel detector based on the depth of interaction. *IEEE Trans. Nucl. Sci.* **69**, 1773–1779 (2022). <https://doi.org/10.1109/TNS.2022.3170427>
26. Z. He, R.D. Vigil, Investigation of pixelated HgI₂ γ -ray spectrometers. *Nucl. Instrum. Meth. A* **492**, 387–401 (2002). [https://doi.org/10.1016/S0168-9002\(02\)01127-0](https://doi.org/10.1016/S0168-9002(02)01127-0)

Springer Nature or its licensor (e.g. a society or other partner) holds exclusive rights to this article under a publishing agreement with the author(s) or other rightsholder(s); author self-archiving of the accepted manuscript version of this article is solely governed by the terms of such publishing agreement and applicable law.